

Effect of impurities on the optical properties of KTP single crystals grown from flux

Hamideh Zaliani^{1,*}, Majid Ja'far Tafreshi¹, Dariush Souri²

¹ Department of Physics, Semnan University, Semnan, Iran

² Department of Physics, Faculty of Science, Malayer University, Malayer, Iran

*Corresponding author: E-mail address: zaliani8388@gmail.com

Abstract:

In the present work, KTP crystals have been grown by spontaneous nucleation technique in flux medium using $K_6P_4O_{13}$ flux. 0.4-1 °C/h cooling rates were applied in the spontaneous nucleation process. The presence and amount of impurities has been determined by using XRF. The optical transmission spectra of impure KTP crystals in the UV–Visible region are discussed. The transmission cut-off is clearly shown at the optical absorption edge, as well as the rapidly reduced absorption with increasing wavelength. It is shown that the presence of impurity shifts the absorption edge of KTP towards lower energy region. The wavelength dependence of absorption coefficient α is determined in the UV–visible range, and the characteristics of the optical absorption edge are discussed. Results reveal that the absorption edge and the type of optical charge carrier transition can be attributed to indirect transition for these crystals. It is shown that presence of impurity decreases the indirect band gap (E_g) of KTP crystals, causing the indirect transition absorption edge to move towards lower energy. Also, structural characterization was carried out employing XRD and IR analysis, confirming the growth of KTP crystal.

Keywords: Spontaneous nucleation method, KTP crystals, Energy gap, Transmission spectrum, Flux method.

PACS: 61, 78

اثر ناخالصی ها بر خواص نوری تک بلورهای KTP رشد یافته از فلاکس

حمیده ذالیانی^۱، مجید جعفر تفرشی^۱، داریوش سوری^۲

^۱ گروه فیزیک، دانشگاه سمنان، سمنان

^۲ گروه فیزیک، دانشگاه ملایر، ملایر

چکیده

در کار حاضر، بلورهای KTP بروش هسته بندی خودبخودی در محیط فلاکس با استفاده از فلاکس $K_6P_4O_{13}$ رشد یافته اند. در فرایند هسته بندی خودبخودی، نرخهای سرمایش در گستره ۰/۴ °C/h تا ۱ °C/h اعمال شده اند. حضور و میزان ناخالصی ها با استفاده از XRF تعیین شده است. طیف عبوردهی نوری بلورهای KTP ناخالص در ناحیه فرابنفش-مرئی مورد بحث واقع می شود. علاوه بر کاهش سریع جذب با افزایش طول موج، قطع عبور دهی در لبه جذب نوری بوضوح مشهود است. نشان داده می شود که حضور ناخالصی لبه جذب را به

انرژیهای بالاتر انتقال می دهد. وابستگی طول موجی ضریب جذب α در گستره فرابنفش-مرئی تعیین می گردد و مشخصه های لبه جذب نوری بحث می شود. نتایج نشان می دهند که لبه جذب و نوع گذار نوری حامل بار را می توان در نمونه های مورد مطالعه به گذار غیر مستقیم نسبت داد. نشان داده می شود که حضور ناخالصی، گاف نواری غیر مستقیم (Eg) بلورهای KTP را کاهش می دهد و باعث میل لبه جذب به سمت انرژیهای کم می گردد. همچنین، مشخصه نگاری ساختاری با بکارگیری XRD و تحلیل IR انجام شد که موید رشد بلور KTP می باشد.

واژه های کلیدی: روش هسته بندی خودبخودی، بلورهای KTP، گاف انرژی، طیف عبوردهی، روش فلاکس.

1. Introduction

Excellent characteristics like high thermal stability, good mechanical properties, transparency over a large wavelength range, large nonlinear-optical coefficients, high damage threshold, and broad angular acceptance have made potassium titanyl phosphate (KTiOPO₄; KTP) as an excellent crystal for second-harmonic conversion of Nd:YAG laser radiation [1-2]. The presence of impurities in KTiOPO₄ (KTP) single crystals can have severe consequences in the performance of devices made from these crystals, for example the optical absorption in the green-wavelength regime leads to a detrimental effect on their SHG performance [3], so the characterization of the spectroscopic properties of impurities in bulk crystals is important.

Because of KTP decomposes upon melting at 1172 °C, its growth in the single-crystal is mainly done by two main growth methods, namely, the hydrothermal method and the flux method [4-10]. The flux method seems to be superior to the hydrothermal method in almost every respect such as quality, size, growth velocity and costs [11-12]. In addition, although this method has the disadvantages of incorporation of OH⁻, but is currently the most popular method for obtaining large KTP single crystals. Among the choices from phosphates, tungstates, molybdates, etc. as solvent, poly-phosphate K₆P₄O₁₃ has been identified as the most suitable for the crystal growth of KTP crystals because it does not contain any ion different from those in KTP [9]. But even after avoiding the possibility of impurity incorporation in the crystal by choosing this self-flux, one is left with at least two more possibilities of contamination. One, of course, is from the starting chemicals, and the other one is through impurities from the crucible [3].

There are many reports on the growth and quality of KTP crystals [13-21]; they reported that KTP crystals of adequate quality for the applications mentioned have been grown from a potassium-phosphate flux

system (especially $K_6P_4O_{13}$) [13], Bolt et al. [13] and Halfpenny et al. [14] showed low dislocation density in flux grown KTP, which was investigated by means of X-ray topography using characteristic X-ray radiation and synchrotron white radiation, respectively. Yokotani *et al.* [15] showed that optically uniform devices could be obtained when a single growth sector which was chosen by means of laser interferometry was used. However, Sasaki *et al.* [16] found that each sector had a distribution of refractive indices and had problems obtaining large areas for nonlinear devices.

In the present study, single crystals of $KTiOPO_4$ were grown using the slow cooling flux method in the three and single-zone furnace system. It was observed that transmission window of KTP crystals are very wide ranging. We have three purposes in present work; the first is studying of the optical spectrums and determining peaks, the second is to reveal impurities by XRF analysis and the third is to consider effect of these peaks and so impurities on band gap of crystals. There have been reports that some kinds of impurities, such as Si, Al, Ca, Pb, Fe and Nb are responsible for absorbance in KTP [17]. In our grown KTP crystals, the XRF analysis reveal these impurities at the threshold detection level. However, the Pt and Rh impurities were detected and measured to be 0.06%.

2. Crystal growth experimental details

KTP single crystals were grown by the flux growth technique without a seed crystal. The prepared raw material and flux (K_6 flux) are mixed in a definite ratio and a suitable amount of the mixture is put into an open platinum crucible consist of 5-10% Rh with 50 mm in diameter and 50 mm in height. The purities of the initial components were in the 99.5% - 99.95% range. The assembly is heated to 1050 °C to melt the mixture, and then crystal growth is carried out. The growth of the KTP crystals was accomplished by slow cooling in an appropriate temperature gradient [22]. The properties of growth (for KTP1, KTP2, KTP3 and KTP4 samples) have been presented in Table 1.

3. Characterization

3.1. Optical spectroscopy

The grown crystals were cut and were polished into small specimens of thickness about 1mm and subjected to optical transmission measurements in the spectral region of 300–800 nm using a Shimadzu (UV-PC-3101) UV–VIS spectrophotometer. A large number of KTP crystals were examined during this study. The transmission spectra for different samples in different status are shown in Figs 1-4. In these figures, we show the optical transmission spectra of KTP crystals grown by spontaneous nucleation and nucleation on rod.

3.2. XRF analysis

X-ray fluorescence (XRF) studies were carried out using Bruker diffractometer XRF "Germany" to check the presence of impurities in the grown crystals [3]. The impurities percent for different samples show in Table 2.

The presence of some expected impurities has been confirmed; Rh is diffused from the crucible walls. Other unexpected impurities were also found, the most significant one being Si and then Al. Small concentrations of Fe, Ca, Pb and Nb have also been determined. Also XRF analysis carried out on the Pt crucible used for the growth of colored crystals of KTP confirmed the presence of Rh impurity in the crucible. Thus the crucible used for growing this particular crystal was identified as the source of Rh impurity in the crystal. The Pt and Rh impurities were detected and measured to be 0.06%.

3.3. XRD analysis

The structural characterization of the KTP samples was carried out by x-ray diffractometry (XRD) using a Bruker diffractometer (AXS D8 Advance, $\text{CuK}\alpha$: 1.5406 Å). XRD pattern of typical sample KTP3 is shown in Figs. 5 (a and b), to confirm the growth of KTP crystal and existence of Rh impurity, respectively.

3.4. IR analysis

The FTIR absorption spectrum of the produced KTP crystal was recorded at room temperature on a Shimadzu 8400S system over a spectral range of 400-4000 cm^{-1} , to determine the structural units and therefore to confirm the growth of KTP crystal. Typical plot of IR spectra is presented in Fig. 6.

4. Band gap and absorption cut off

Incorporation of impurity ion considerably decreases the overall transmittance of KTP and it can be explained by the increases of absorption coefficient (α), which can be evaluated by Mclean formula [13]. Miyamoto *et al.* [17] have reported that the incorporation of Pt impurities from the crucible increases the optical absorption coefficient of KTP [23].

In the low energy area, α is proportional to $\exp(h\nu)$, while in the high energy field, α obeys the following relationship:

$$(\alpha(\nu)h\nu) \propto (h\nu - E_{\text{gap}})^m \quad (1)$$

where, E_{gap} and $h\nu$ are the optical gap and incident photon energy, respectively; $\alpha(\nu)$ is the absorption coefficient defined by the Beer–Lambert’s law as:

$$\alpha(\nu) = (2.303/d)A \quad (2)$$

where, d and A are the sample thickness and sample absorbance, correspondingly [19]. Also, m is the index which determines the type of optical charge carrier transmission.

In order to obtain E_{gap} (upon Eq.1), it is necessary to measure the absorption coefficient (α) which is carried out by measuring the film thickness and film absorbance. In this work, we use the absorption spectrum fitting method (ASF) [24] to obtain the band gap avoiding the film thickness measurement which commonly could not be measured precisely.

Thus, applying the ASF method, from Eq. (1) and Eq. (2) we have [24]:

$$\left(\frac{A}{\lambda}\right)^{1/m} \propto \left(\frac{1}{\lambda} - \frac{1}{\lambda_g}\right) \quad (3)$$

where, E_g is the optical energy gap, $m = 1/2$ for direct transition and $m = 2$ for indirect transition. KTP is an indirect gap material [5], thus the m -value for KTP is 2, which this optimized value was obtained by examination of the different values of m , by using the least square technique.

Thus the value of band gap, in eV, can be calculated from the parameter λ_g using $E_{gap} = 1239.83/\lambda_g$ in other word, the value of λ_g can be calculated by extrapolating the linear region of $(A/\lambda)^{1/2}$ vs. $(1/\lambda)$ curve at $(A/\lambda)^{1/2} = 0$. The variation of $(A/\lambda)^{1/2}$ vs. $(1/\lambda)$ was plotted for the present samples, as shown in Figs. 7-10; the data of optical band gap for different samples have been listed in Table 3.

5. Discussion

Some crystals grown in platinum crucible containing Rh as impurity were reddish-orange in color. Because of platinum being soft, sometimes manufacturers add rhodium deliberately to increase the strength of the platinum crucible. The platinum group metals require rather complex aqueous chemical processing for their isolation [25]. This increases the probability of occurrence of Rh in Pt crucible. Because of the growth period of KTP crystal is high, Rh ions get into the molten charge through diffusion. Repeat growth runs performed from the old charge from the same crucible result in more reddish colored crystals [3].

The band edge of KTP has been reported to lie between 340 and 360 nm [26-27]. UV cut off for pure KTP crystal shows, unlike the colored crystal. From Figs. 7-10, it is seen that the incorporation of impurity ions such as Rh shift the absorption edge of KTP towards UV region by 30 nm. The UV band edge is generally attributed to absorption in the Ti—O subgroup [28-29].

It was observed in transmission spectra More than 50% transmission for specimens of thickness exceeding 1mm for crystals grown by nucleation from K_6 flux. Incorporation of impurity ions considerably decreases

the overall transmittance of KTP. We saw that incorporation of some impurities from flux and raw materials to crystals is low and it didn't affect on transmission percent and just created some low new peak. For more clarity, it should be mentioned that in KTP1, KTP2 and KTP3 samples which have been grown by the same method (SN), results are (a): upon the XRF analysis, the percent of the principle components increased with decreasing of cooling rate; (b): impurities contents decreased with decreasing of cooling rate; (c): optical transmittance of the mentioned samples increased with decreasing of cooling rate, thus it affects directly on the optical band gap (namely, caused to the decreasing of E_g as could be predicted. On the other hand, in KTP4 which has been grown by NR method, the percent of the principle components are comparable with what reported for KTP1, 2 and 3 samples; but using this growth method (as improved method), we have the following results: (a): impurities contents decreased; (b): optical transparency and optical transmission increased.

Generation of visible laser wavelengths by SHG of near-IR-wavelength laser beams is a frequent application of KTP. A comparison of transmission at the SHG wavelengths of the 1.064 mm Nd:YAG fundamental laser lines was made for this reason. The SHG wavelength (532 nm) is in the region of reduced transmission [28].

The optical spectra in the 400-700 nm regions are of specific interest in KTP. The absorption in the 500 nm region is probably due to the presence of Ti^{+3} in different concentrations. The same absorption is induced by electric fields in KTP and was assumed to correspond with the grey track effect [30-34]. Use of KTP as a second-harmonic generator (SHG) to convert 1064 nm to 532 nm requires a minimum absorption at 532 nm. This absorption is probably involved in the grey track formation mechanism. The presence of Ti^{+3} in phosphate glasses has been shown to result in a broad absorption band over the 400-700 nm region [35]. It was suggested that the absorption near 400 nm or 390 nm may be due to either Fe^{2+} or Fe^{4+} ions [36-38] that we observed this ions at the XRF data, too. Scripsick et al attribute the 500 nm band to the gray-track effect that gray tracks are formed in flux-grown KTP when isolated Fe^{3+} ions trap holes and Ti^{4+} ions (with an adjacent oxygen vacancy) trap [39].

The major peaks are at 450, 560 and 725 nm. These absorptions are due to a charge-transfer transition in $\text{Ti}^{+3}\text{-Ti}^{+4}$ pairs (450 nm) and the other two to the Jahn-Teller effect which causes a tetragonal distortion in the octahedral coordination polyhedron. It is well known that when two ions occupy adjacent, identical lattice sites in an insulating crystal, transfer of an electron between them does not involve a change in energy. In this case, there would be no optical absorption. However, if the ions are on different sites, an energy difference does exist and optical absorption will be observed; This is probably the case for Ti^{+3} and Ti^{+4} ions in KTP, so the presence of Ti^{+3} in KTP as the source for this absorption [34]. The presence of an impurity such as Pb or Rh could cause a reduction in the oxidation state of Ti^{+4} to Ti^{+3} and also increase the concentration of K vacancies. All of these factors could result in an increased susceptibility of KTP to grey track damage [31]. In addition, as presented in Figs. 5-a and b, XRD outputs confirm the growth of KTP crystal and the presence of small amount of Rh impurity. Fig. 5-a was in excellent matching with the 35-0802 standard and the presence of RhO_2 impurity was checked, which was in relatively good matching with the standard code of 43-1026; XRD outputs show an orthorhombic structure with the lattice parameters of $a= 12.814 \text{ \AA}$, $b=10.816 \text{ \AA}$ and $c= 6.404 \text{ \AA}$. On the other hand, to more confirm the growth of KTP crystals, IR study was performed and spectrum of the sample grown from K_6 flux is shown in Fig. 6; main absorption bands are located at about 409, 432, 468, 489, 505, 557, 596, 640, 708, 787, 821, 831, 976, 1004, 1026, 1049, 1101, 1124, 1650, 2380 and 3500 cm^{-1} . For example, vibration modes especially around 1049, 1101 and 976 cm^{-1} are related to PO_4 tetrahedral units and the band of 1124 justify the presence of P-O bonds. Also, absorption peaks of 409, 596 and 708 are in consistency with TiO_6 octahedra [17]. Bands of 1650, 2380 and 3500 cm^{-1} are related to H_2O due to small ambient and sample humidity. In brief, IR output confirm and justify again the growth of KTP crystal from flux.

6. Conclusions

Transmission measurements in KTP were performed. XRF studies confirmed the incorporation of impurity content in the crystals grown from kind of fluxes.

The incorporation of impurity ions into the grown crystal is presumed to shift the optical absorption edge towards the UV region and increases the optical absorption. Structural elucidation was carried out employing XRD and IR analysis, confirming the growth of KTP crystals.

Acknowledgement

The authors gratefully acknowledges Mrs Elaheh Gharibshahian for her technical support.

7. Reference:

[1] F C Zumsteg, J D Bierlein, T E Gier *J. Appl. Phys.* **47** 4980 (1976)

۲- محمد جابری، امیر حسین فرهبد و حمید رحیم پور سلیمانی؛ مجله پژوهش فیزیک ایران، جلد ۱۳، شماره ۱، بهار ۱۳۹۲، صفحه ۳۵

[3] I Bhaumik, S Ganesamoorthy, R Bhatt, A K Karnal, R Sundar, V K Wadhawan *Cryst. Res. Technol.* **41** 1180 (2006)

[4] J C Jacco, G M Zioacono, M Jaso, G Mizell, B Greenberg *J. Cryst. Growth.* **70** 484 (1984)

[5] C V Kannan, S Ganesamoorthy, S Kumaragurubaran, C Subramanian, R Sundar, P Ramasamy *Cryst. Res. Technol.* **37** 1049 (2002)

[6] P F Bordui, S Motakef *J. Cryst. Growth.* **96** 405 (1989)

[7] T Sasaki, A Miyamoto, A Yokotani, S Nakai *J. Crystal. Growth.* **128** 950 (1993)

[8] S Ganesamoorthy, F Josephkumar, S Balakumar, C Subramanian, P Ramasamy *Mat. Sci. Eng. B* **60** 88 (1999)

[9] G M Loiacono, T F McGee, G Kostecky *J. Cryst. Growth.* **104** 389 (1990)

[10] I Bhaumik, S Ganesamoorthy, R Bhatt, R Sundar, A K Karnal, V K Wadhawan *J. Cryst. Growth.* **243** 522 (2002)

[11] L P Shi, J Chrosch, J W Wang, Y G Liu *Cryst. Res. Technol.* **27** 76 (1992)

[12] S Haussuhl, S Luping, W Banlia, W Jiyang, J Liebertz, A Wostrack, C Fink *Cryst. Res. Technol.* **29** 583 (1994)

[13] R J Bolt, H De Haas, M T Sebastian, H Klapper *J. Crystal Growth.* **110** 587 (1991)

-
- [14] P J Halfpenny, L O Neill, J N Sherwood, G S Simpson, A Yokotani, A Miyamoto, T Sasaki, S Nakai *J. Crystal. Growth.* **113** 722 (1991)
- [15] A Yokotani, A Miyamoto, T Sasaki, S Nakai *J. Crystal Growth.* **110** 963 (1991)
- [16] T Sasaki, A Miyamoto, A Yokotani, S Nakai *J. Cryst. Growth.* **129** 950 (1993)
- [17] E Gharibshahian, M J Tafreshi, M Fazli *Indian J. Pure Appl. Phys.* **47** 356 (2009)
- [18] E Gharibshahian, M J Tafreshi *Cryst. Res. Technol.* **50 (8)** 603 (2015)
- [19] J R Ghandhi, M Rathnakumari, P Muralimanohar, P Sureshkumar, G Bhagavannarayana *J. Appl. Crystallography* **47** 931 (2014)
- [20] J R Ghandhi, B Vijayalakshmi, M Rathnakumari, P Sureshkumar *Journal of Minerals & Materials Characterization & Engineering* **10 (8)** 683 (2011)
- [21] J R Ghandhi, M Rathnakumari, K Ramamurthi, R R Babu, D Sastikumar, P Sureshkumar *Optik* **125** 6462 (2014)
- [22] A Miyamoto, Y Mori, T Sasaki *Appl. Phys. Lett.* **69** 1032 (1996)
- [23] CV Kannan, S Ganesamoorthy, H Kimura, A Miyazaki *J. Crystal. Growth* **279** 403 (2005)
- [24] D Souri, K Shomalian *J. Non-Crys. Solids* **355** 1597 (2009)
- [25] K De, *A Textbook of Inorganic Chemistry* (Wiley Eastern Limited, New Delhi), 7th edition, 1992
- [26] D Bierlein, H Vanherzeele *J. Opt. Soc. Am. B* **6** 622 (1989)
- [27] V V Lemeshko, V V Obukhovskiy, V Stoyanov, N I Pavlova, A I Pisanskiy, P A Korotkov *Ukrain. Fiz. Zh.* **31** 1746 (1986)
- [28] G Hansson, H Karlsson, S Wang, F Laurell *Appl. Optics.* **39** 5058 (2000)
- [29] J C Jacco, G M Loiacono *Appl. Phys. Lett.* **58** 560 (1990)
- [30] R Blachman, P F Bordui, M M Fejer *Appl. Phys. Lett.* **64** 1318 (1994)
- [31] G M Loiacono, D N Loiacono, T McGee, M Babb *J. Appl. Phys.* **72** 2705 (1992)
- [32] M G J Roelofs *Appl. Phys.* **65** 4976 (1989)

-
- [33] K Terashima, M Takeda, M Kawachi *Jpn. J. Appl. Phys.* **30** 497 (1991)
- [34] N B Angert, V M Garmash, N I Pavlova, A V Tarasov *Sov. J. Quantum Electron.* **21** 426 (1991)
- [35] L E Bausa, J G Sole, A Duran, J M F Navarro *J. Non-Cryst. Solids* **127** 267 (1991)
- [36] M J Martin, D Bravo, R Sole, F Diaz, F J Lopez, C Zaldo *J. Appl. Phys.* **76** 7510 (1994)
- [37] M J Martin, C Zaldo, F Diaz, R Sole, D Bravo, F J Lopez *Radiat. Eff. Defects Solids* **136** 243 (1995)
- [38] L E Halliburton, M P Scricsick *SPIE*. **235** 2379 (1995)
- [39] M P Scricsick, D N Loiacono, J Rottenberg, S H Goellner, L E Halliburton, F K Hopkins *Appl. Phys. Lett.* **66** 3428 (1995)

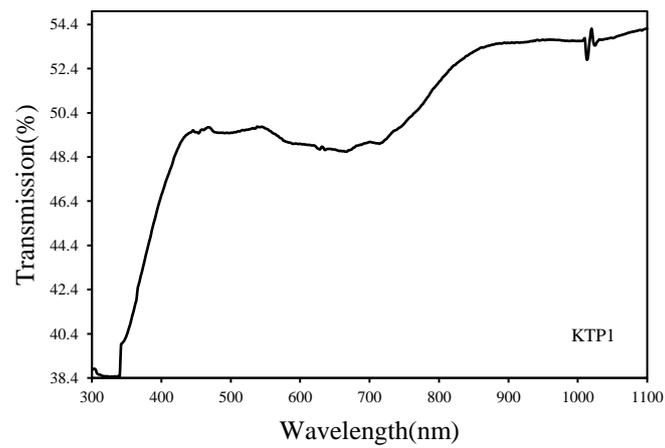


Fig. 1: The optical transmission spectrum of KTP crystal grown from K_6 flux by spontaneous nucleation with cooling rate of $1\text{ }^\circ\text{C/h}$; KTP1

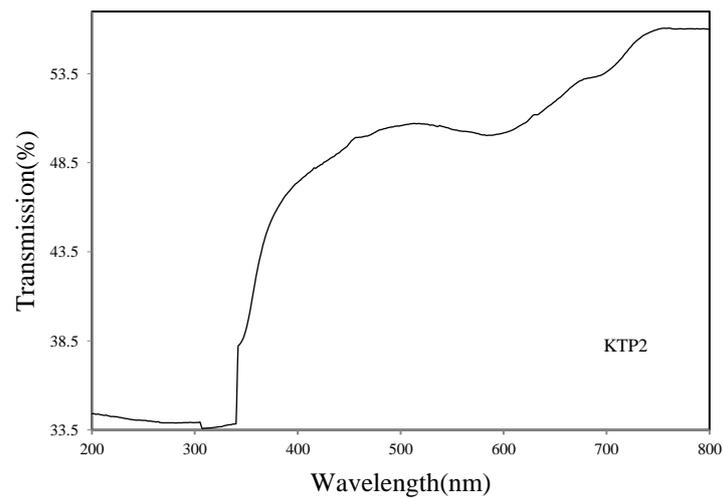


Fig. 2: The optical transmission spectrum of KTP crystal grown from K_6 flux by spontaneous nucleation with cooling rate of $0.8\text{ }^\circ\text{C/h}$; KTP2

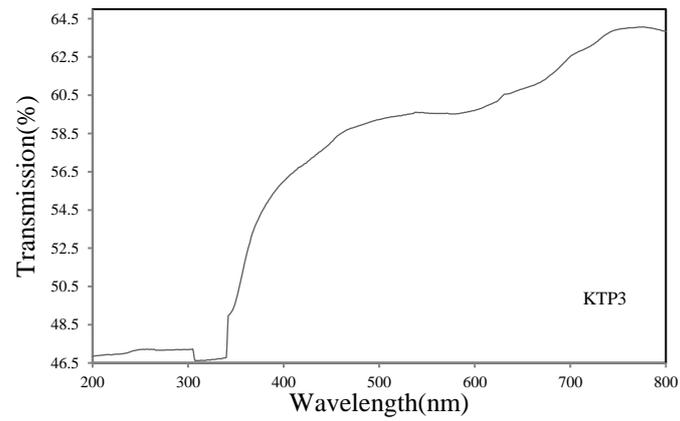


Fig. 3: The optical transmission spectrum of KTP crystal grown from K_6 flux by spontaneous nucleation with cooling rate of $0.4\text{ }^\circ\text{C/h}$; KTP3



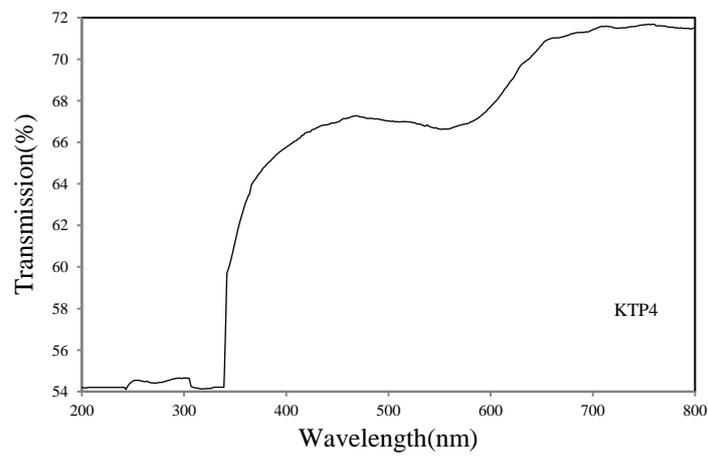


Fig. 4: The optical transmission spectrum of KTP crystal grown from K_6 flux by nucleation on rod with cooling rate of $0.7\text{ }^\circ\text{C/h}$; KTP4

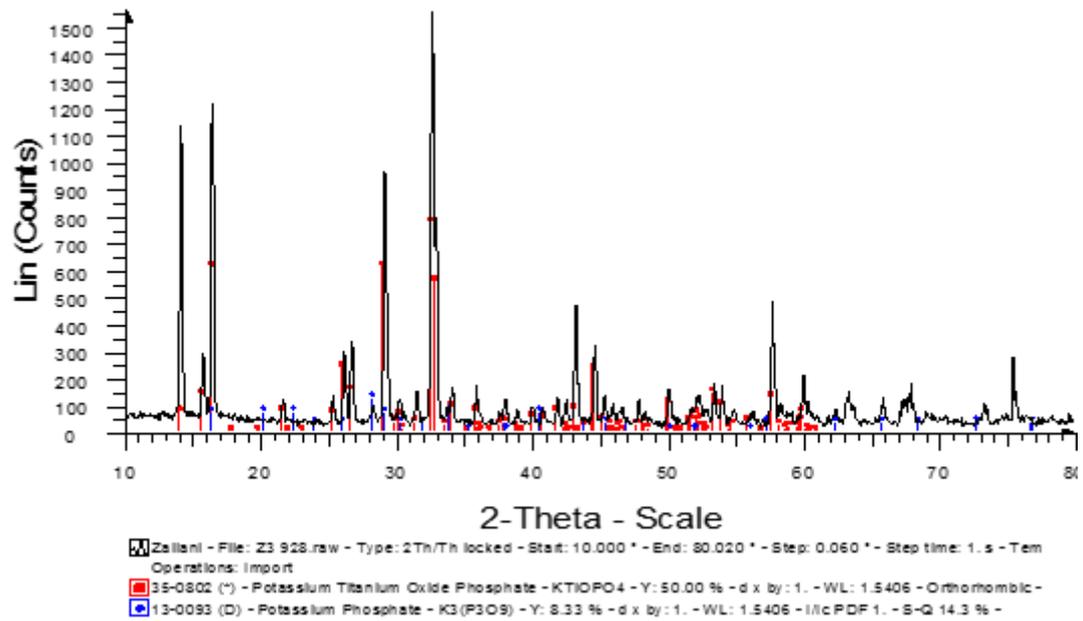

a

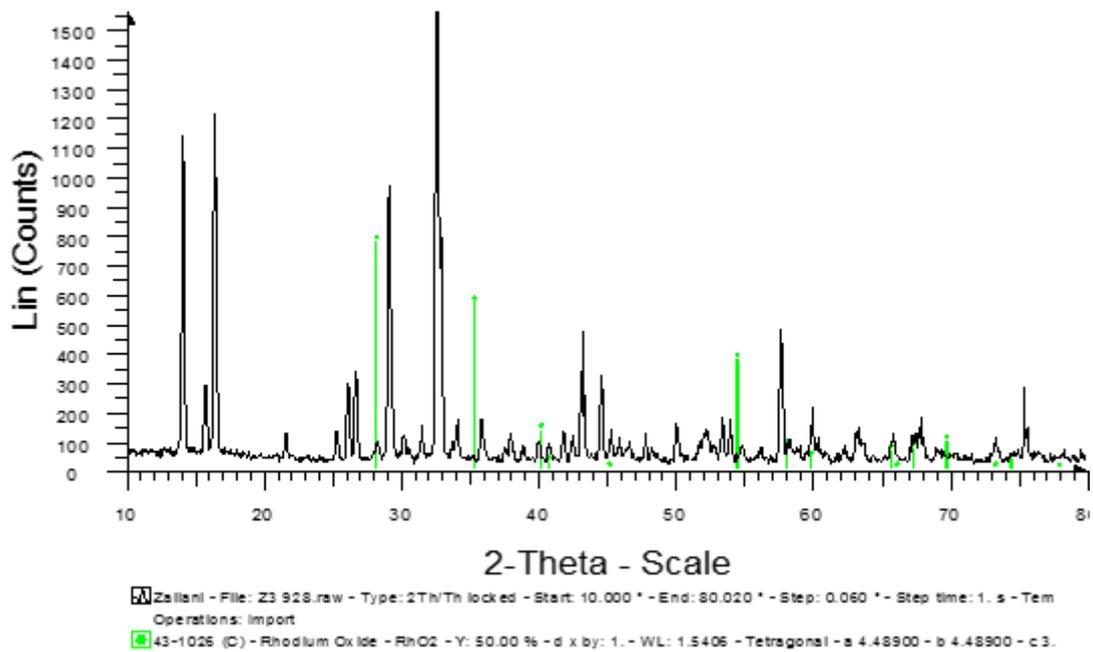

b

Fig. 5: XRD patten of KTP3 sample: a) to confirm the growth of KTiPO₄ crystal, b) to detect the existence of RhO₂ impurity.

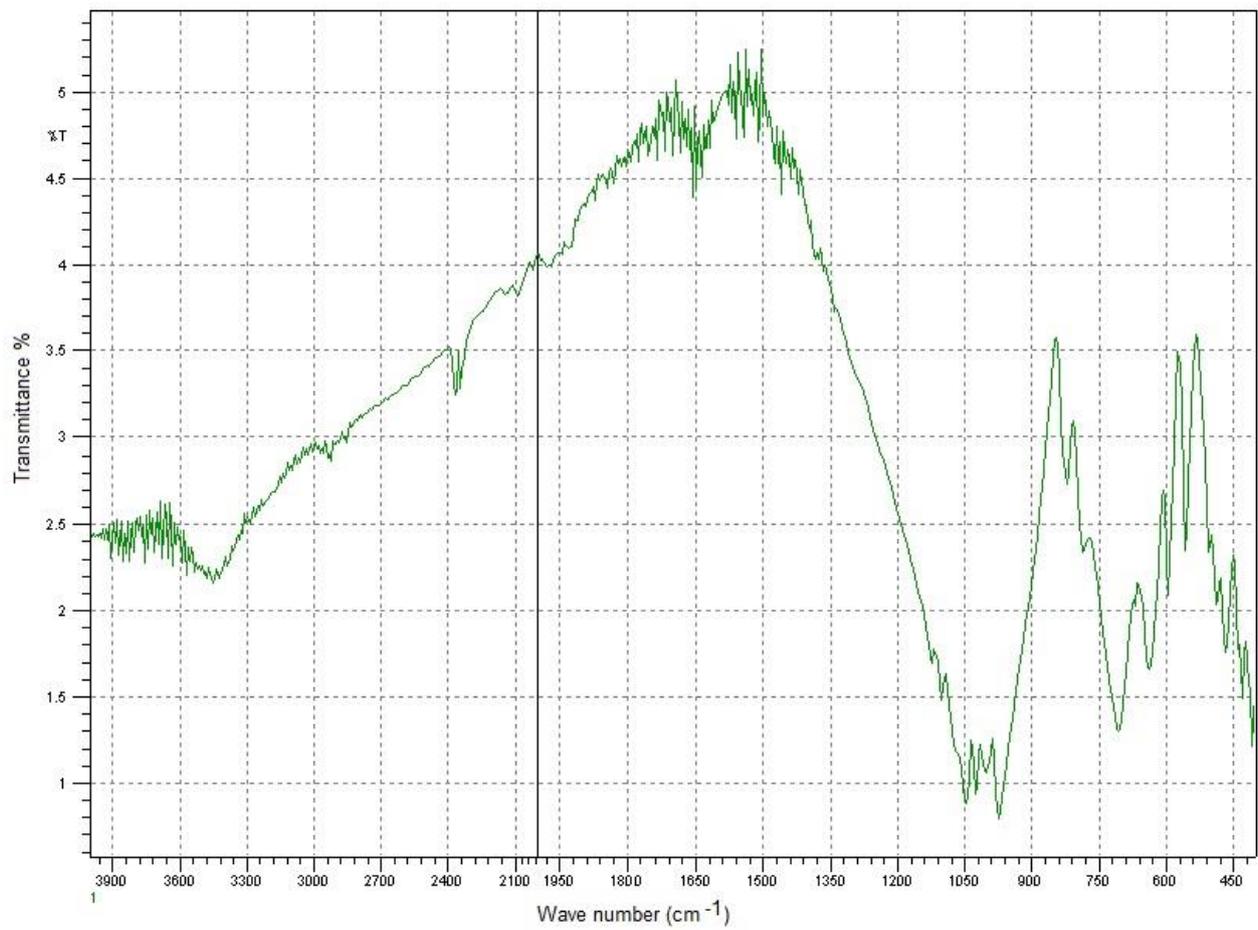


Fig. 6: IR spectrum of KTP crystal grown from K₆ flux.

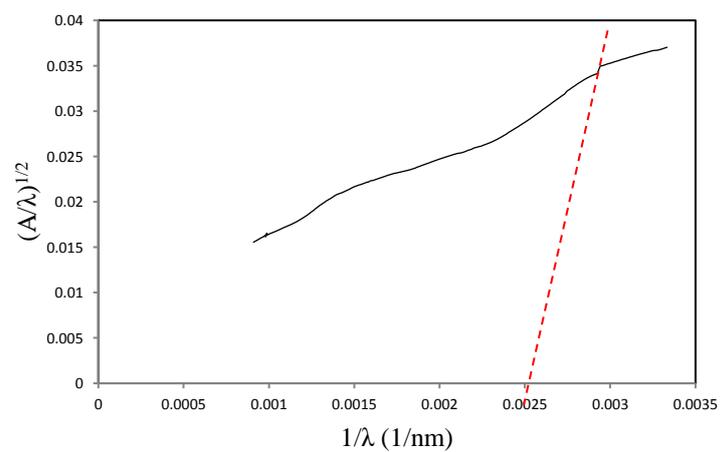


Fig. 7: The absorption spectrum of KTP crystals grown from K₆ flux by spontaneous nucleation with cooling rate of 1°C/h; KTP1

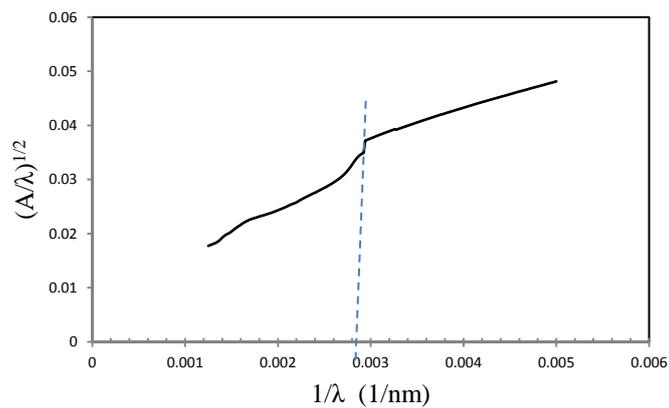


Fig. 8: The absorption spectrum of KTP crystals grown from K_6 flux by spontaneous nucleation with cooling rate of 0.8 °C/h; KTP2

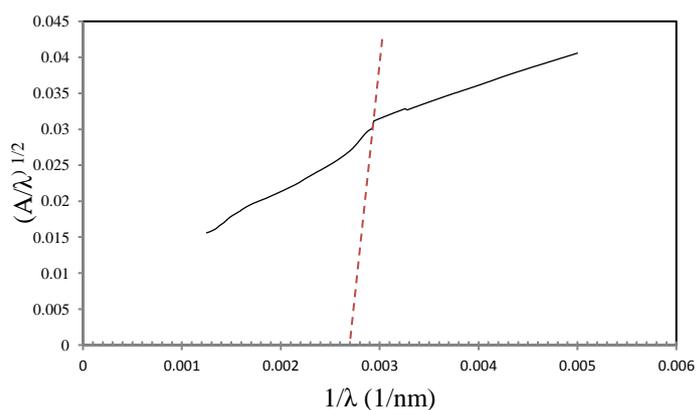


Fig. 9: The absorption spectrum of KTP crystals grown from K_6 flux by spontaneous nucleation with cooling rate of 0.4 °C/h; KTP3

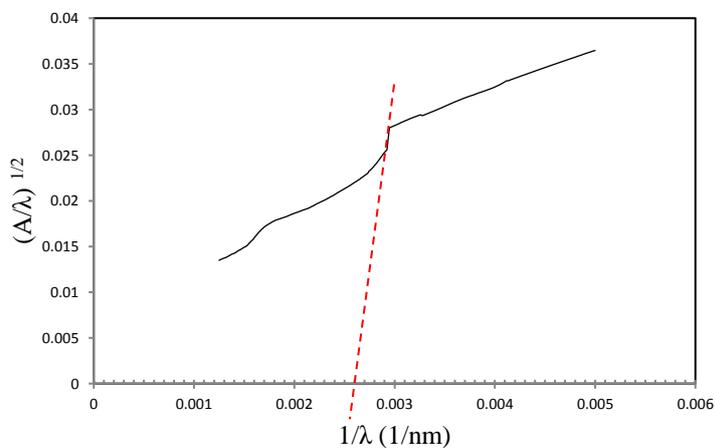


Fig. 10: The absorption spectrum of KTP crystals grown from K_6 flux by nucleation on rod with cooling rate of 0.7 °C/h; KTP4

Table 1: The properties of growth for four samples

Samples	Growth technique	Cooling rate (°C/h)	Growth time (h)	Transmission (%)
KTP1	Spontaneous Nucleation (SN)	1	170	53.67%
KTP2	Spontaneous Nucleation(SN)	0.8	250	56.055%
KTP3	Spontaneous Nucleation(SN)	0.4	307.5	64.02%
KTP4	Nucleation on Rod (NR)	0.7	182	71.631%

Table 2: The different impurities percent for KTP samples

Sample	KTP1	KTP2	KTP3	KTP4
Element's oxide				
Nb ₂ O ₅	0.010%	0.011%	0.014%	0.010%
Fe ₂ O ₃	0.034%	0.026%	0.070%	0.029%
CaO/PbO	0.046% (CaO)	0.049% (CaO)	0.11% (CaO)	0.095% (PbO)
Al ₂ O ₃	0.20%	0.19%	0.38%	0.12%
SiO ₂	0.654%	0.597%	1.09%	0.40%
K ₂ O	22.45%	22.31%	25.66%	22.01%
P ₂ O ₅	28.6%	29.9%	32.1%	28.1%
TiO ₂	33.46%	34.45%	40.16%	33.89%

Table 3: Energy band gap of different samples

samples	Cooling rate (°C/h)	λ_g (nm)	E_{gap} (eV)
KTP1	1	342	3.63
KTP2	0.8	355	3.50
KTP3	0.4	377	3.29
KTP4	0.7	360	3.45