# Synthesis of high transparency of F doped NiO monocrystalline thin films by spray deposition

## Mounira Mammi<sup>1</sup>, Said Benramache<sup>2</sup>, Yacine Aoun<sup>3</sup>, and Amira Sbaihi<sup>2</sup>

1Department of Physics, University of El-Oued, 39000, Algeria.

2 Laboratoire des Matériaux, des Énergies et de l'Environnement, University of Biskra 07000, Algeria 3 Mechanical Department, Faculty of Technology, University of El-Oued, El-Oued 39000, Algeria

E-mail: s.benramache@univ-biskra.dz,

#### Abstract

The main objective of this work is to investigate a new material based on fluorine doped NiO thin films by spray deposition technique. Nickel nitrate hexahydrate Ni(NO<sub>3</sub>)<sub>2</sub>.6H<sub>2</sub>O and ammonium fluoride (NHF4) with a ratio of F/Ni = 0.04 were used to prepare F doped NiO. The structural, optical and electrical properties of F doped NiO thin films were investigated with different NiO:F solution volumes of 5, 10, 15 and 20 ml using the spray technique. The prepared F doped NiO thin films have a monocrystalline nature with a cubic structure; the (111) diffraction peak is the preferred orientation; the maximum crystallite size is 19.21 nm obtained for 20 ml. The optical property shows that the all the prepared F doped NiO thin films have a good transmittance of about 80 % in the visible region. The F doped NiO thin films deposited with 20 ml have a minimum optical gap energy of 3.51 eV and the highest value of Urbach energy of 0,689 meV. However, the thin film prepared with 5 ml has a minimum electrical resistivity of 231  $\Omega$ .cm, which can be used as a gas sensing.

Keywords: F; NiO; Thin films; Spray deposition technique; Monocrystalline structure.

## 1. Introduction

Recent research shows that semiconductor metal oxides are essential compounds for the development of ultrahigh frequency devices, photocatalysis, optoelectronics, gas sensors, lithium ion microbatteries and cathode materials for alkaline batteries [1-3]. However, nickel oxide (NiO) is a direct large-gap (3.6-4.0 eV), semi-transparent p-type semiconductor material with a wide range of applications, represented by gas sensors, ultraviolet photo detectors, dye-sensitizers, photocatalysis, photovoltaic coatings, and lightweighting [1-6], the structural components in aerospace, in ceramic structures, counter electrodes and the anode layer of solid electrode oxide fuel cells [2–9]. On the other hand, nickel oxide has a cubic structure and NiO has a good transparency in the thin film [10-12]. NiO has recently focused on doping NiO with transition metals (TMs) such as Cu [2], Na [3], Zn [4], V [6], Mn [10], Al, Ga, In [12], Li [13], Ag [14], Mg [15], Co [16], and Mo [17] in cooperation with Ni to increase electrical conductivity. However, there is a new doping effect on optical properties; which is fluorine doped NiO thin films.

The F doping can be used to increase the transmission and to increase the movement of F in the NiO:F.

The aim of this work is to study F doped NiO thin films with the help of organic solar cells for electrical energy harvesting. The organic solar cells consisted of an inner mirror layer inside (ITO glass) and a substrate holder. F doped NiO thin films can be deposited on a glass substrate by the spray pneumatic method with different volumes of 5, 10, 15 and 20 ml of the NiO:F mixture. The F doped NiO thin films were characterised by various methods, including X-ray diffraction, UV-vis spectrophotometry, and four-point techniques.

## 2. Experiments

The prepared solution of NiO was dissolved by  $0.10 \text{ mol.l}^{-1}$  of nickel nitrate hexahydrate Ni(NO<sub>3</sub>)<sub>2</sub>.6H<sub>2</sub>O (industrial powder with 99 purity) and ammonium fluoride (NHF<sub>4</sub>) (industrial powder with 97 purity) with the ratio of F/Ni = 0.04, the mixture powder was dissolved in the same volumes absolute of water H<sub>2</sub>O, we have added drops of HCl solution for stabilisation.





Figure 1 A photograph of the experimental setup for the deposition of F-doped NiO thin films.

The mixture solution was stirred and heated at 45°C until a time of 4 h to transparent solution. F doped NiO thin films were sprayed onto the heated glass substrates at 450 °C with different solution volumes using the organic solar cells, and the volumetric spray rate was 0.1 ml/s. The structure of the spray deposition system and the fabricated organic solar cells are shown in **Figure 1**. In this work, we used a digital display thermocouple (C100FK02 - M\*AN) to determine the temperature, which it determined between 400 and 600 °C. However, the direct calcinations of Ni(NO<sub>3</sub>)<sub>2</sub> 6H<sub>2</sub>O follows the reaction as:

$$2Ni(NO_3), 6H_2O = 2Ni + 4NiO_2 + 4NO_2 + O_2 + 12H_2O$$
 (1)

The thin films of F doped NiO were characterised by different techniques to find the crystalline structure, optical transmission and electrical conductivity, which it are the respectively the X-ray diffraction (XRD Bruker AXS-8D with  $\lambda=0.15406$  nm), spectrophotometer (UV-Lambda 35 with 300–900 nm of wavelength), and the four point techniques of the instrument Keithley Model 2400 Low Voltage Source Meter instrument.

### 3. Results and discussion

**Figure 2** shows the crystal structure of F-doped NiO thin films prepared at different NiO:F solution volumes of 5, 10,15 and 20 ml and NiO at 10 ml.

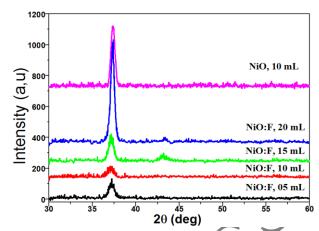


Figure 2 The results of X-ray diffraction spectra of undoped and F-doped NiO thin films at different NiO:F volumes.

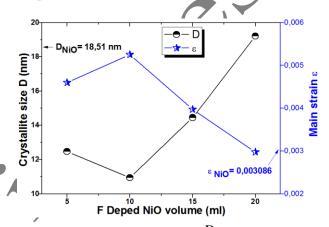


Figure 3 The results of crystallite size D (111) and main strain  $\mathcal E$  of F undoped and doped NiO thin films at different NiO:F volumes.

As a first result, we have found that all the films exhibited a diffraction peak at  $2\theta = 37$  related to the (111) plane of the NiO phase, which is a single crystal cubic structure. It can be seen that the thin film of F doped NiO deposited with 20 ml has a good crystal structure showed for a highest and strong peak, which confirm that the increase in the deposition volume can be improve the crystalline quality of F doped NiO thin films.

The crystal structure of F-doped NiO thin films represented by crystallite size D (111) and main strain  $\mathcal{E}$  was calculated using the following equations [16-18]:

$$D = \frac{0.9\lambda}{\beta \cos \theta} \tag{2}$$

$$\varepsilon = \frac{\beta}{4\tan\theta} \tag{3}$$

where D is the crystallite size,  $\lambda$  is the X-ray wavelength ( $\lambda = 1.5406~\text{A}^\circ$ ),  $\beta$  is the full width at half-maximum (FWHM), and  $\theta$  is the angle of diffraction peak and  $\mathcal E$  is the main strain.

**Figure 3** shows the variation of the crystallite size and the main strain of F doped NiO thin films at different volumes. As can be seen, as the volumes increases, the variation of the crystallite size is inversely with to the main strain (see **Table 1**), which is can be explained by the variation of the FWHM.

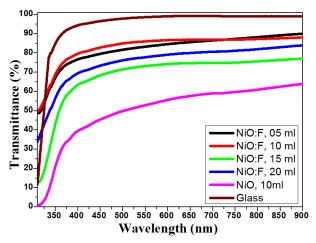


Figure 4 The results of the transmission spectra's of undoped and F doped NiO thin films at different NiO:F volumes

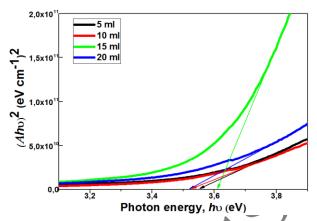


Figure 5a The typical variation of values  $(AhV)^2$  as a function of photon energy hV of F doped NiO thin films deposited at different NiO:F volumes, used to determine the optical band gap energy.

Table 1 Shows the crystal structure of F doped NiO thin films representing of the diffraction angle, FWHM, the crystallite sizes, the lattice parameter a and main strain of the (111) plane of undoped and F doped NiO thin films as a function of NiO:F volume.

Samples	Diffraction angle $2 heta$ (°)	FWHM $eta$ (°)	Crystallite size $D$ (nm)	Lattice parameter $a$ (nm)	Main strain ${\cal E}$
NiO, 10 ml	37.37	0.54	18.51	0,44144	0.00308
NiO:F, 05 ml	37,21	0,80	12.47	0,442662	0,00459
NiO:F, 10 ml	37,09	0,91	10.94	0,44205	0,00525
NiO:F, 15 ml	37,15	0,69	14.45	0,44032	0,00397
NiO:F, 20 ml	37,32	0,52	19,21	0,43982	0,00298

Table 2 Shows the average transmittance and Film thickness of undoped and F doped NiO thin films as a function of NiO:F volume.

Samples	NiO, 10 ml	NiO:F, 05 ml	NiO:F, 10 ml	NiO:F, 15 ml	NiO:F, 20 ml	Glass
Average Transmittance (%) 400-800 nm	53.6	83.9	85.6	73.8	78.0	98
Film thickness (nm)	160	110	112	134	140	/

Where, the maximum crystallite size is 19.21 nm obtained for 20 ml, this is can be explained by the homogeneous in the surface and coalescence, which it's corresponded in the minimum value of lain strain (see **Table 1**). However, the undoped NiO thin film has a main strain of 0.00308 and a crystallite size of 18.51 nm.

The optical properties of undoped and F doped NiO thin films were represented by the transmission spectra in the range of 300 to 900 nm of wavelength. **Figure 4** shows the variation of the transmission of the deposited thin films at different NiO and NiO:F volumes. As the NiO:F volume increased, the transmission was decreased due to the increase in the film thickness. However, the prepared F doped NiO thin films have a good transmission is about 80 % in the visible region due to the fluorine doping (see **Table 2**). The transmittance of 20 ml (78%) high then the 15 ml (73.8%) due to the crystallinity of the film .The region exist between 300 and 400 nm, it is the region of strong absorption, heir the transmission of F doped NiO decreased due to the excitation and the migration of the electrons from the conduction band to the valence band.

The optical band gap energy of the thin films of undoped and F doped NiO was calculated from transmission spectra, which it was applied the following equations [18-20].

$$A = \alpha d = -\ln T \tag{4}$$

$$(Ah\upsilon)^2 = B(h\upsilon - E_{g}) \tag{5}$$

where  $E_g$  the optical band gap energy; A is the absorbance, d is the film thickness; T is the transmission spectra of thin films;  $\alpha$  is the absorption coefficient values; B is a constant and hv is the photon energy. It was found by the extrapolating the curve of  $(Ahv)^2$  vs hv at A=0 [21], which the variation was indicated in **Figure 5a**, show the drawn of the  $(Ahv)^2$  as a function of hv of F doped NiO thin films. However, the Urbach energy of F doped NiO thin films has been determined by the following expression [21,22]:

$$A = A_0 \exp(\frac{h\nu}{E_u}) \tag{6}$$

where  $A_0$  is a constant and  $E_u$  is the Urbach energy, Figure 5b shows the variation of the drawn of LnA as a function of the photon energy hv, where the Urbach energy was deduced by the inverse of the slope of the curve.

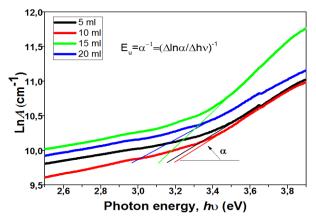


Figure 5b The typical variation of values LnA as a function of photon energy  $h\nu$  of F doped NiO thin films deposited at different NiO:F volumes, used to determine the Urbach energy.

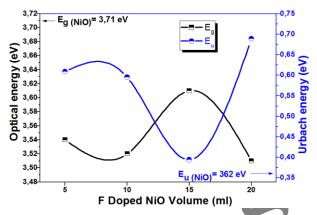


Figure 6 The results of optical band gap  $E_u$  and Urbach energy  $E_u$  of F doped NiO thin films at different NiO:F volumes.

Table 3 Shows the optical properties such as the variation of optical band gap energy and Urbach energy of undoped and F doped NiO thin films as a function of NiO:F volume.

Samples	Optical gap energy ${\cal E}_g^{}$ (eV)	Urbach energy $E_u$ (eV)
NiO, 10 ml	3.71	0.362
NiO:F, 05 ml	3,54	0,609
NiO:F, 10 ml	3,52	0,595
NiO:F, 15 ml	3,61	0,394
NiO:F, 20 ml	3,51	0,689

Table 4 Shows the electrical characterisations such as the variation of measured current and voltage and the sheet resistance of F doped NiO thin films as a function of the NiO:F volume.

Samples	Measured Current I (nA)	Measured voltage $V$	Sheet resistance $R_{sh}$ ( $\Omega$ )	Electrical resistivity $ ho$ ( $\Omega$ .cm)
NiO, 10 ml	0.011	5	1.1x10 <sup>10</sup>	1.5x10 <sup>5</sup> Ω.cm
NiO:F, 05 ml	۱۰,۸۰		2.1x10 <sup>7</sup>	231 Ω.cm
NiO:F, 10 ml	۰٫۱۳	5	1.7x10 <sup>9</sup>	$1.9 \mathrm{x} 10^3  \Omega.\mathrm{cm}$
NiO:F, 15 ml	٠,٠٨٠		2.8x10 <sup>9</sup>	3.8x10 <sup>3</sup> Ω.cm
NiO:F, 20 ml	٠,٠٨٧		2.6x10 <sup>9</sup>	3.6x10 <sup>3</sup> Ω.cm

Table 5 The comparative study of the structural, optical and electrical properties of undoped and F doped NiO thin films.

Table 5 The comparative study of the structural, optical and electrical properties of undoped and F doped NiO thin films.							
Thin films	Experiments	Film thickness (nm)	Crystallite size G (nm)	Transmittance (%)	Optical Band Gap Eg (eV)	Sheet resistance or electrical resistivity	Ref.
NiO NiO: 1F% NiO: 5F% NiO: 10F%	-Spray deposition ST=400 °C -0.1M -0.3 mL/s		25 35 21.9 13.5	75 75+1 75+2 75+2	3.67 3.72 3,71 3.72	18 Ωcm 2 Ωcm 14 Ωcm 18 Ωcm	[23]
NiO NiO: 1Li% NiO: 2Li% NiO: 3Ll% NiO: 4Li% NiO: 5Li%	- Spray deposition - ST= 500 °C -0.1M -13 mL	197 236 221 374 435 421	41 59 31 45 44 36	59 32 48 37 50 47	3.865 3.744 3.697 3.738 3.714 3.716	$^{-}$ 2.403x10 $^{9}$ Ω 1.195x10 $^{7}$ Ω 7.984x10 $^{6}$ Ω 1.386x10 $^{7}$ Ω 1.694x10 $^{7}$ Ω	[24]
NiO NiO: 1Cu% NiO: 2Cu% NiO: 3Cu% NiO: 4Cu% NiO: 5Cu%	- Spray deposition - ST= 410 °C -0.2 M	-	64 37 51 38 51 57	about 50	3.572 3.519 3.536 3.461 3.473 3.467	2712 Ωcm 589 Ωcm 490 Ωcm 1106 Ωcm 545 Ωcm 669 Ωcm	[25]
NiO, 10ml NiO:F, 05ml NiO:F, 10ml NiO:F, 15ml NiO:F, 20ml	- Spray deposition - ST=400 °C - 0.1M - F/Ni = 4%	160 110 112 134 140	18.51 12.47 10.94 14.45 19.21	53.6 83.9 85.6 73.8 78.0	3.71 3,54 3,52 3,61 3,51	1.5x10 <sup>5</sup> Ω.cm 231 Ω.cm 1.9x10 <sup>3</sup> Ω.cm 3.8x10 <sup>3</sup> Ω.cm 3.6x10 <sup>3</sup> Ω.cm	This Work

**Figure 6** shows the variation of the band gap energy and the Urbach energy of newly deposited F doped NiO thin films at different volumes. As can be seen, as the volumes increases, the variation of the optical energy is inversely with the Urbach energy (see **Table 3**). The film deposited with 20 ml has a minimum optical energy and maximum Urbach energy, this is can be explained by the increased movement of F in the NiO:F, and the corporation between F and O and thus there is an increase in the substitutional site. However, the undoped NiO thin film has a highest the optical energy of 3.71 eV and a minimum the Urbach energy of 0.362 eV (see **Table 3**).

The electrical conductivity of F doped NiO thin films was determined by four- point probe technique, it is based on the measured voltage, current and sheet resistance expressed by:

$$R_{sh} = \frac{1}{d} \left( \frac{\pi}{\ln 2} * \frac{V}{I} \right) \tag{7}$$

$$\sigma = \frac{1}{\rho} = \frac{1}{dR_{sh}} \tag{8}$$

where  $R_{sh}$  is the electrical resistivity; d is the film thickness;  $\sigma$  is the conductivity;  $\rho$  is the resistivity; V is the applied voltage =5V and I is the measurement current (see **Table 4**). As can be seen, as the volume increases, the electrical resistivity increases from 5 to 15 ml (see **Table 4**), this increase can be explained by the decrease in the number of electrons and mobility, leading to a p-type semiconductor. However, the undoped NiO

thin film has a highest electrical resistivity of  $1.5 \times 10^5$   $\Omega$ .cm and the F doped NiO thin film with 5 ml has a minimum the electrical resistivity of 231  $\Omega$ .cm (see **Table 3**).

The comparative study of the structural, optical and electrical properties of undoped and F doped NiO thin films are presented in **Table 5**, as can be seen, we have a lowest crystallite size, good transmittance and good electrical property.

## 4. Conclusion

In the conclusion, the structural, optical and electrical properties of undoped F doped NiO thin films were investigated. The thin films of F doped NiO were deposited by spray technique at substrate temperature of 450 °C with different NiO:F solution volumes of 5, 10, 15 and 20 ml. The prepared F doped NiO thin films have a monocrystalline nature with a cubic structure, the (111) diffraction peak is the preferred orientation, the maximum crystallite size is 19.21 nm obtained for 20 ml. The optical property shows that the all the prepared F doped NiO thin films have a good transmittance which is about 80 % in the visible region. The F doped NiO thin films deposited with 20 ml have minimum optical gap energy of 3.51 eV and the highest value of Urbach energy is 0,689 meV. However, the thin film prepared with 5 ml has a minimum electrical resistivity of 231  $\Omega$ .cm, which can be used as a gas sensing.

### 5. References

- 1. M.H. Raza, K. Movlaee, Y. Wu, S.M. El-Refaei, M. Karg, S.G. Leonardi, G. Neri, N. Pinna, Tuning the NiO Thin Film Morphology on Carbon Nanotubes by Atomic Layer Deposition for Enzyme-Free Glucose Sensing, ChemElectroChem 6 (2019) 383–392.
- 2. S.H. Wang, S.R. Jian, G.J. Chen, H.Z. Cheng, J.Y. Juang, Annealing-Driven Microstructural Evolution and Its Effects on the Surface and Nanomechanical Properties of Cu-Doped NiO Thin Films, Coatings 9 (2019) 107.
- 3. Y. Aoun, M. Marrakchi, S. Benramache, B. Benhaoua, S. Lakel, A. Cheraf, Preparation and Characterizations of Monocrystalline Na Doped NiO Thin Films, Materials Research 21(2018) e20170681.
- 4. C. Zaouche, A. Gahtar, S. Benramache et al. The determination of urbach energy and optical gap energy by many methods for Zn doped NiO thin films fabricant semiconductor by spray pyrolysis, Digest Journal of Nanomaterials & Biostructures (DJNB) 17 (2022) 1453-1461.
- 5. R.S. Kate, S.C. Bulakhe, R.J.Deokate, Effect of Substrate Temperature on Properties of Nickel Oxide (NiO) Thin Films by Spray Pyrolysis, Journal of Electronic Materials 48 (2019) 3220–3228.
- 6. V. Panneerselvam, K.K. Chinnakutti, S.T. Salammal, A.K. Soman, K. Parasuraman, V. Vishwakarma, V. Kanagasabai, Role of copper/vanadium on the optoelectronic properties of reactive RF magnetron sputtered NiO thin films, Applied Nanoscience 8 (2018) 1299–1312.
- 7. Muzamil Aftab, M.Z. Butt, Dilawar Ali, Farooq Bashir, Z.H. Aftab, Impact of copper doping in NiO thin films on their structure, morphology, and antibacterial activity against Escherichia Coli, Ceramics International, 46 (2020) 5037-5049
- 8. M.Sh. Abdel-wahab, H.K. El Emam and W.M. A. El Rouby, Sputtered Cu-doped NiO thin films as an efficient electrocatalyst for methanol oxidation, RSC Advances 13 (2023) 10818-10829
- K. Sato, S. Kim, S. Komuro and X. Zhao, Characteristics of Cu-doped amorphous NiO thin films formed by RF magnetron sputtering, Japanese Journal of Applied Physics 55 (2016) 06GJ10
- 10.N.R. Aswathy, JiJi Varghese, Shree Ranjini Nair, R. Vinod Kumar, Structural, optical, and magnetic properties of Mn-doped NiO thin films prepared by sol-gel spin coating, Materials Chemistry and Physics 282 (2022) 125916.
- 11.H.S. Rasheed, H.I. Abdulgafour, F.M. Hassan et al. Synthesis, characterization, and gas-sensing performance of macroporous Zn-doped NiO thin films for ammonia gas detection, Journal of Materials Science: Materials in Electronics 33 (2022) 18187–18198.
- 12., I.L.P. Raj, , S. Valanarasu, , A. Asuntha et al. Development of a highly sensitive UV sensor using Al, Ga, and In-

- doped NiO thin films via nebulizer spray pyrolysis method for photodetector applications, Journal of Materials Science: Materials in Electronics 33 (2022) 11753–11767.
- 13. X. Chu, J. Leng, J. Liu et al. Effect of annealing conditions on the structural, electrical and optical properties of Lidoped NiO thin films, Journal of Materials Science: Materials in Electronics 27 (2016), 6408–6412.
- 14. M.S. Abdel-wahab, H.K El Emam. & W.M.A. El Rouby, Sputtered Ag-doped NiO thin films: structural, optical, and electrocatalytic activity toward methanol oxidation Journal of Materials Science: Materials in Electronics 34 (2023) 1637.
- 15. Y. Zhao, J. Yan, Y. Huang et al. Interfacial self-assembly of monolayer Mg-doped NiO honeycomb structured thin film with enhanced performance for gas sensing, Journal of Materials Science: Materials in Electronics 29 (2018) 11498–11508
- 16.R.S. Kate, S.C. Bulakhe & R.J. Deokate, Co doping effect on structural and optical properties of nickel oxide (NiO) thin films via spray pyrolysis, Optical and Quantum Electronics 51 (2019) 319.
- 17.H.H. Abdelhalium, M.S. Abdel-wahab, M.T. Tamm et al. Highly, efficient ultraviolet photodetector based on molybdenum-doped nanostructured NiO/ITO thin film, Applied Physics A 129 (2023) 459.
- 18. A. Diha, S. Benramache, L. Fellah, The Crystalline Structure, Optical and Conductivity Properties of Fluorine Doped ZnO Nanoparticles, J. Nano- Electron. Phys. 11 (2019) 03002.
- 19. A. Kumar, P.P. Sahay, Lithium doping in spray-pyrolyzed NiO thin films: results on their microstructural, optical and electrochromic properties, Applied Physics A 127 (2021) 286.
- 20. A. Gahtar, S. Benramache, A. Ammari, A. Boukhachem, A. Ziouche, Effect of molar concentration on the physical properties of NiS thin film prepared by spray pyrolysis method for supercapacitors, Inorganic and Nano-Metal Chemistry 52 (2022) 112-121.
- 21.U. Alver, H. Yaykaşlı, S. et Kerli al. Synthesis and characterization of boron-doped NiO thin films produced by spray pyrolysis, International Journal of Minerals, Metallurgy and Materials 20 (2013) 1097–1101.
- 22. H. Aydin, S.A. Mansour, C. Aydin et al. Optical properties of nanostructure boron doped NiO thin films, Journal of Sol-Gel Science and Technology 64 (2012) 728–733.
- 23.S. Kerli, and U. Alver, Effect of F Doping on Structural, Electrical, and Optical Properties of NiO Thin Films, Crystallography Reports 59 (2014) 1103–1106.
- 24. D.P. Joseph et al. Spray deposition and characterization of nanostructured Li doped NiO thin films for application in dye-sensitized solar cells, Nanotechnology 19 (2008) 485707.
- 25.M.Aftab, M.Z. Butt, D. Ali, F. Bashir, T.M. Khan, Optical and electrical properties of NiO and Cu-doped NiO thin films synthesized by spray pyrolysis Optical Materials 119 (2021) 111369.

